

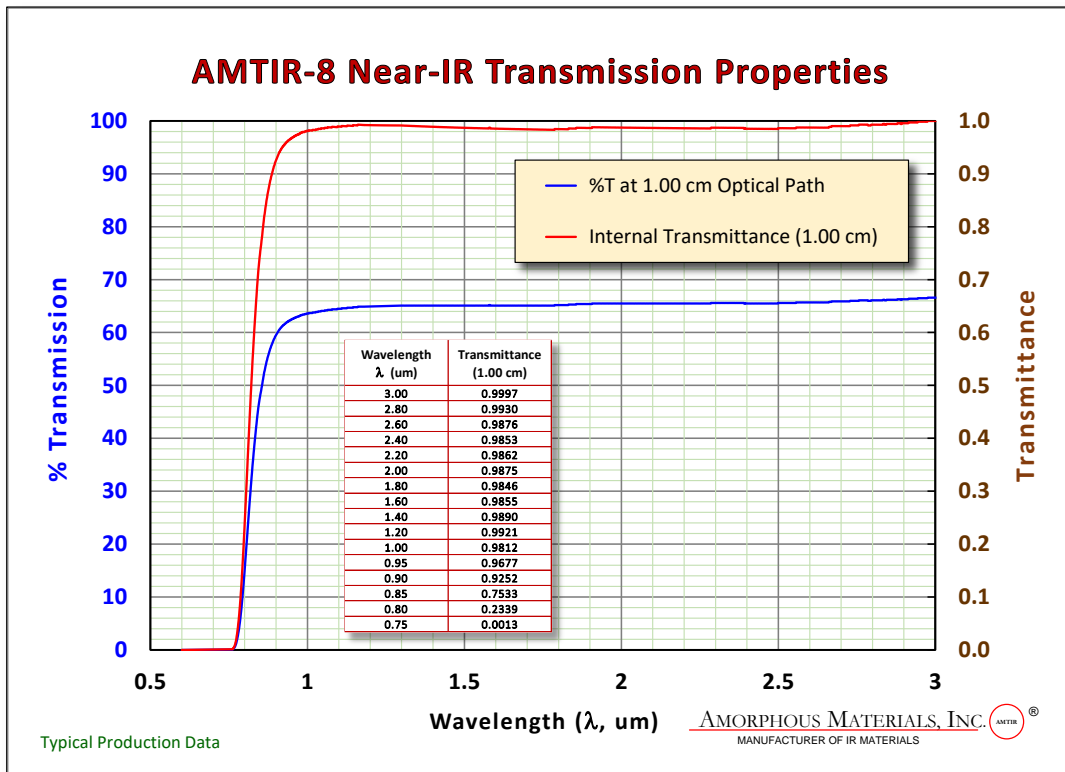


AMTIR-8 Material Properties		
PROPERTY	METRIC UNITS	ENGLISH UNITS
Composition	GeAsSe	
Glass Transition Temperature (T _g)	136 °C	277 °F
Annealing Temperature	144 °C	291 °F
Dilatometric Softening Point	159 °C	318 °F
Upper Use Temperature	123 °C	253 °F
Thermal Expan. Coeff. (-150 to 25 °C)	21.3 ppm / °C	11.8 ppm / °F
Thermal Expan. Coeff. (25 to 100 °C)	23.8 ppm / °C	13.2 ppm / °F
Specific Heat	cal/gm-°C (J/gm-°K)	0.074 (0.0031)
Thermal Conductivity	5.8 x 10 ⁻⁴ cal /sec-cm-°K	1.41 x 10 ⁻¹ BTU/ Hr-ft-°F
Knoop (Vickers) Hardness	170 (153)	
Young's Modulus (E)	19.8 GPa	2.87 x 10 ⁶ lbs /in ²
Shear Modulus (G)	7.72 GPa	1.12 x 10 ⁶ lbs/ in ²
Poisson's Ratio	0.282	
Tensile Strength	7.6 MPa	1100 lbs / in ²
Compressive Strength	145 MPa	21,000 lbs / in ²
Rupture Modulus (ASTM-C158)	16.9 MPa	2445 lbs / in ²
Density	4.53 gm/cm ³	283.2 lbs/ft ³
Dielectric Constant	8.1	
Resistivity (@100Hz)	>1 x 10 ¹² ohm-cm	>4 x 10 ¹¹ ohm-in
Stress Opt. Coeff. (avg Tens. & Comp.)	3 to 12 um, x10 ⁻¹² m ² /N	10
Refractive Index @ 3 um (20.5 °C)	2.62289	
Refractive Index @ 8 um (20.5 °C)	2.60799	
Refractive Index @ 12 um (20.5 °C)	2.59820	
SWIR Abbe Value	1 to 2 um	20.2
MWIR Abbe Value	3 to 5 um	190
LWIR Abbe Value	8 to 12 um	164
Δn/ΔT @ 3 um	< 11 ppm/ °C	
Δn/ΔT @ 8 um	< 8 ppm/ °C	
Δn/ΔT @ 12 um	< 7 ppm/ °C	
Chemical Durability (weight loss in milligrams for 100 gm sample in a 4 Hour Period)		
Solution	Temperature (°C)	Milligrams
H ₂ O	90 °C	0
2% NH ₄ OH	60 °C	10
2% KOH	60 °C	25
HCl, H ₂ SO ₄ , HNO ₃ & EtOH (all conc)	60 °C	0 to 0.02


NOTE: All data provided on these datasheets are typical melt values and believed to be accurate and representative of standard AMI melt practice, at the time of publication. Industry standard tolerances apply to all categories. Current maximum blank size available meeting standard quality specifications is Ø150 mm x 25 mm thick. (Larger diameters may be available in the future.)

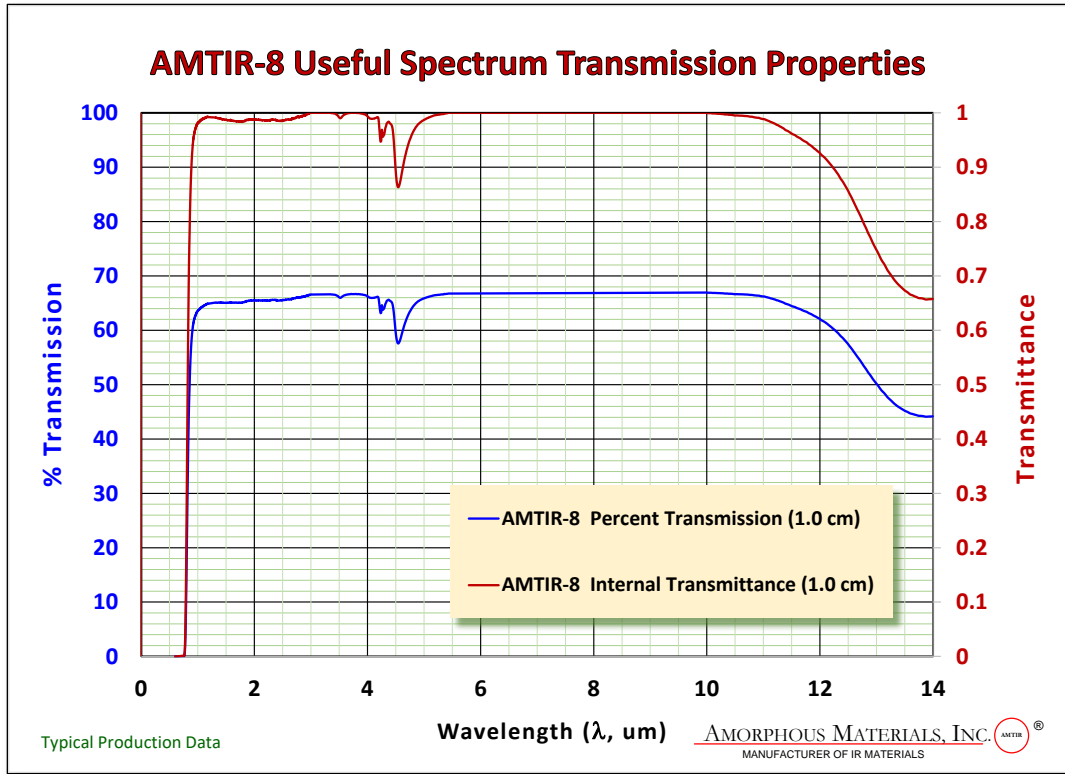

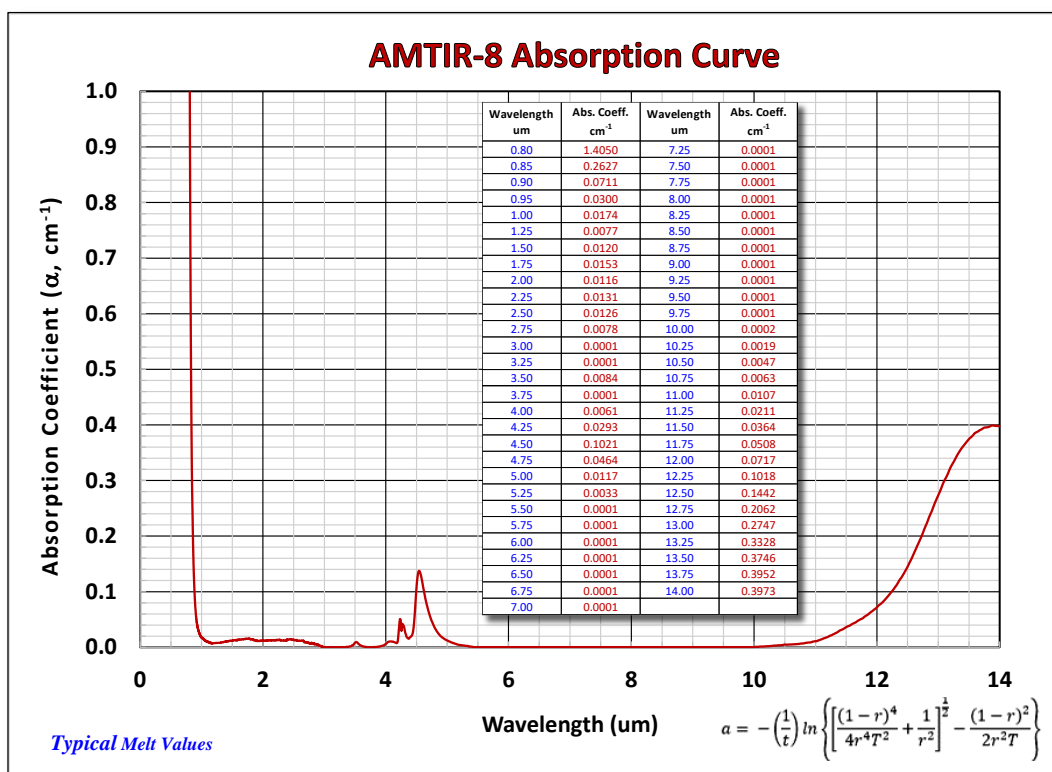

Wavelength (μm)	Fresnel Coefficient	Transmission (%) (2.54 cm)	Transmittance (2.54 cm) (corrected)	Absorption Coefficient (cm ⁻¹)
1.000	0.648	63.57	0.981	0.0174
2.000	0.663	65.48	0.988	0.0116
3.000	0.666	66.57	0.999	0.0001
4.000	0.667	66.24	0.993	0.0061
4.500	0.667	59.78	0.896	0.1021
4.960	0.667	65.68	0.984	0.0147
5.000	0.667	65.90	0.987	0.0117
6.000	0.668	66.77	0.999	0.0001
7.000	0.668	66.81	0.999	0.0001
8.000	0.669	66.85	0.999	0.0001
9.000	0.669	66.89	0.999	0.0001
10.000	0.669	66.93	0.999	0.0002
11.000	0.670	66.22	0.988	0.0107
12.000	0.670	62.07	0.926	0.0717
13.000	0.671	50.13	0.747	0.2747
14.000	0.672	44.17	0.658	0.3973

NOTE: Amorphous Materials, Inc. calculates the values for the Absorption Coefficients, using an approach used routinely by many infrared Optical Engineers. The applicable equation is found on the Absorption Curve. Calculate the ABSORBANCE, at a given wavelength (α), by correcting for multiple-internal reflections (i.e., Fresnel losses) and dividing this value by the light path (i.e., sample thickness in centimeters).

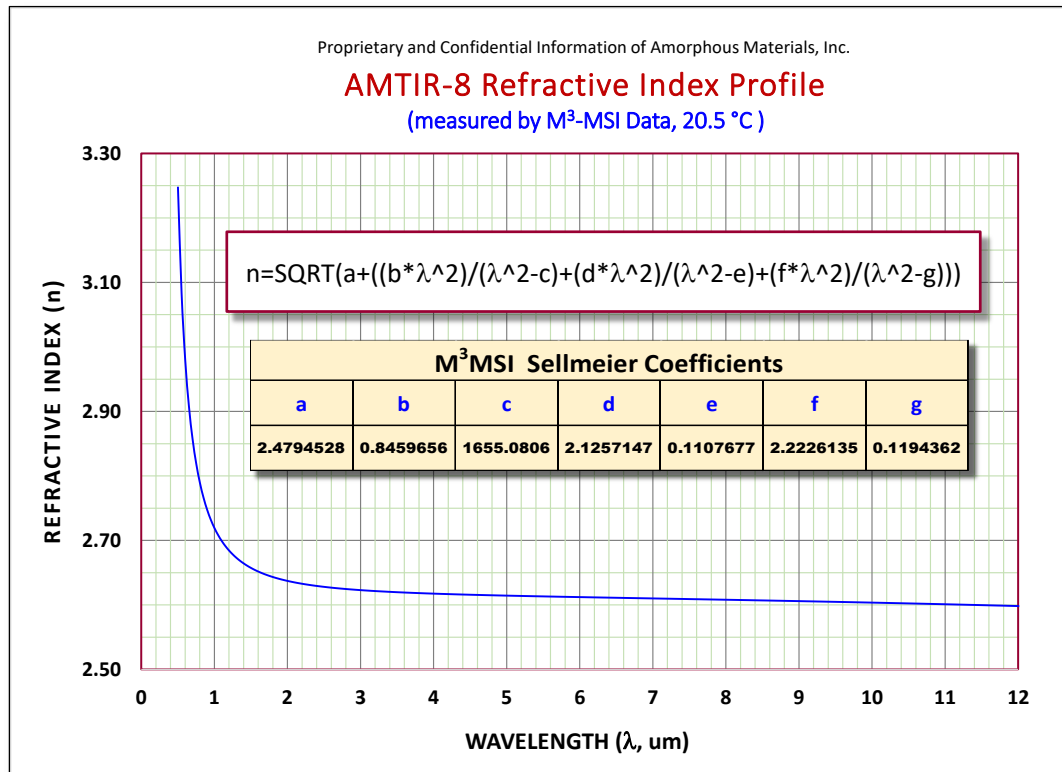

Wavelength (microns)	Refractive Index 20.0 °C	Average $\Delta n / \Delta T$
1.0000	2.71910	0.000017
1.5000	2.65730	0.000015
2.0000	2.63717	0.000013
3.0000	2.62288	0.000011
4.0000	2.61745	0.000009
5.0000	2.61437	0.000009
6.0000	2.61207	0.000008
7.0000	2.61002	0.000008
8.0000	2.60798	0.000008
9.0000	2.60584	0.000008
10.0000	2.60353	0.000007
11.0000	2.60100	0.000007
12.0000	2.59820	0.000007
13.0000	2.59510	0.000007
14.0000	2.59166	0.000007

NOTE: Refractive Index values are typical production values for well-annealed glass and may vary by ±0.0004 (group relative) melt-to-melt. $\Delta n / \Delta T$ values are group relative constants and do not vary significantly in the 6th decimal place.